

Thermally-Assisted Spin-Transfer Torque Magnetization Reversal of Uniaxial Nanomagnets in Energy Space

D. Pinna* and A. D. Kent

Department of Physics, New York University, New York, NY 10003, USA

D. L. Stein

*Department of Physics, New York University, New York, NY 10003, USA and
Courant Institute of Mathematical Sciences, New York University, New York, NY 10012, USA*

The asymptotic behavior of switching time as a function of current for a uniaxial macrospin under the effects of both spin-torque and thermal noise is explored analytically by focusing on its diffusive energy space dynamics. The scaling dependence ($I \rightarrow 0$, $\langle \tau \rangle \propto \exp(-\xi(1-I)^2)$) is shown to confirm recent literature results. The analysis shows the mean switching time to be functionally independent of the angle between the spin current and magnet's uniaxial axes. These results have important implications for modeling the energetics of thermally assisted magnetization reversal of spin transfer magnetic random access memory bit cells.

PACS numbers:

A spin-polarized current passing through a small magnetic conductor is known to deposit its spin-angular momentum into the magnetic system [1, 2]. This in turn causes the magnetic moment to precess and in some cases even switch direction. This has led to sweeping advances in the field of spintronics through the development and study of spin-valves and magnetic tunnel junctions (see, for example, [3]). A thorough understanding of these phenomena, however, requires taking into account the effect of thermal fluctuations inducing diffusion in the moment of a magnetic material. This is of particular experimental relevance since spin-transfer effects on nanomagnets are often conducted at low currents, where noise is expected to dominate. Recent debate in the literature over the proper exponential scaling behavior between mean switching time and current elucidates how the thermally assisted properties of even the simplest magnetic setups leave much to be understood [4–9].

The standard theoretical approach used to study the dynamics of small magnetic structures has been to treat the magnetic system as a macrospin in the spirit of Brown [10], thus modeling the dynamics as those of a magnetic moment undergoing damped precession under the action of an effective field. After Slonczewski [1], one assumes that the magnetic body absorbs spin-angular momentum perpendicularly to its orientation. As such, spin-torque effects are generally taken into account phenomenologically by modifying the macrospin's Landau-Lifshitz-Gilbert (LLG) dynamical equation with the addition of the spin-torque term. The LLG equation for a normalized magnetization $\mathbf{m}$ then reads:

$$\begin{aligned} \dot{\mathbf{m}} = & -\gamma' \mathbf{m} \times \mathbf{H}_{\text{eff}} - \alpha \gamma' \mathbf{m} \times (\mathbf{m} \times \mathbf{H}_{\text{eff}}) \\ & - \gamma' j \mathbf{m} \times (\mathbf{m} \times \hat{\mathbf{n}}_p) + \gamma' \alpha j \mathbf{m} \times \hat{\mathbf{n}}_p, \end{aligned} \quad (1)$$

where $\gamma' = \gamma/(1 + \alpha^2)$, γ is the gyromagnetic ratio, α the Landau damping coefficient and $j = (\hbar/2e)\eta J$ is the spin-angular momentum deposited per unit time with $\eta = (J_\uparrow - J_\downarrow)/(J_\uparrow + J_\downarrow)$, the spin-polarization factor of incident current J . The last two terms describe a vector torque generated by current polarized in the direction $\hat{\mathbf{n}}_p$. The effective field $\mathbf{H}_{\text{eff}}$ is immediately obtained once the energy landscape of the magnetic sample is specified. In the simplified case of a uniaxial monodomain magnet, it is characterized by the projection of the magnetization onto the uniaxial anisotropy axis:

$$U(\mathbf{m}) = -K(\mathbf{m} \cdot \hat{\mathbf{n}}_K)^2 - \mathbf{m} \cdot \mathbf{H}, \quad (2)$$

with $K = (1/2)M_S H_K V$ the uniaxial anisotropy of a magnet of volume V and anisotropy field H_K , saturation magnetization M_S , applied field $\mathbf{H}$, and $\hat{\mathbf{n}}_K$ the unit vector representing the orientation of the uniaxial anisotropy (easy) axis.

Of special interest is the interplay between spin-torque and thermal noise effects. Starting from (1), thermal fluctuations are modeled by considering the effect of a random applied magnetic field with mean zero and variance enforced by the fluctuation dissipation theorem. Doing this leads to a stochastic LLG equation with multiplicative noise [10, 11]. Experimentally, one is generally interested in the magnetization reversal properties of a thin film magnet where the anisotropy axis is out of plane. For currents less than a threshold current (to be defined below), the switching in such magnetic systems appears to be dominated by thermal-activation related reversal processes. Fitting experimental data to theory is complicated by several factors. First, the validity of the macrospin model is questionable for samples typically studied (see, for example, [12]), which are so far larger than the exchange length of transition metals magnets (~ 5 nm). Second, even within the macrospin approximation it is not clear what the relevant energetics are for

*Electronic address: daniele.pinna@nyu.edu

thermally assisted spin transfer torque reversal. This is a consequence of the inherently non-conservative nature of the added spin-torque term which does not allow the construction of a generalized energy landscape suitable for Kramer's theory analysis.

In [9], the authors consider a simplified uniaxial macrospin model where the anisotropy and spin polarization axes were chosen to be collinear. The stochastic evolution equation determining the switching properties of the macrospin could then be described by a single 1D uncoupled equation. In this paper we present a parallel analysis which we believe to be very useful toward the characterization of switching properties in more complex macrospin models where symmetry arguments cannot be found to simplify the general coupled structure of the magnetization evolution equations.

To elucidate the most basic properties of thermally-assisted magnetization reversal under spin-transfer torque, we choose to consider a magnetic system solely characterized by its uniaxial anisotropy and focus on its thermally assisted dynamics in the absence of any applied fields. The energy landscape is given by the first term on the right hand side of (2). The equilibrium states in this landscape are then given by parallel and anti-parallel configurations of the magnetization along the uniaxial anisotropy axis. We consider our magnetic sample to be initially magnetized in thermal equilibrium in one of its two possible stable states (i.e. $m = +\hat{\mathbf{n}}_K$ or $m = -\hat{\mathbf{n}}_K$). Upon applying a (positive) current, spin-torque effects will attempt to drive the magnetization toward aligning with the polarization axis $\hat{\mathbf{n}}_P$. If the current is then switched off again, the magnetization will relax back toward the easy axis. To capture this behavior, it is very helpful to write down the dynamical equation for the projection $q \equiv \mathbf{m} \cdot \hat{\mathbf{n}}_K$ of the magnetization along the easy axis. For temperatures such that $\xi \equiv K/kT \gg 1$, the sign of q will specify to a high degree of accuracy to which state the magnetization will relax after the current is turned off. These "projectional dynamics" read:

$$\begin{aligned} \dot{q} = & \alpha [(n_z I + q)(1 - q^2) + n_x I q s] \\ & + \alpha^2 I n_x m_y + \sqrt{\frac{\alpha}{\xi}} (1 - q^2) \circ \dot{W}, \end{aligned} \quad (3)$$

where $I = j/(\alpha H_K)$ is the normalized current and a natural time unit $\tau = \gamma/H_K t$ has been introduced. If we choose $\hat{\mathbf{n}}_P$ as our z-axis, and $\hat{\mathbf{n}}_K$ oriented somewhere in the x-z plane, then s is the projection of the dynamics on the axis orthogonal to both the y-axis and $\hat{\mathbf{n}}_K$. To simplify the notation, then, n_x and n_z are the components of $\hat{\mathbf{n}}_K$ along the original $\hat{x}$ and $\hat{z}$ axes. The last term appearing in the expression models the effects of thermal noise whose stochastic contribution is intended according to Stratonovich calculus (indicated by the symbol $\circ$) and $\dot{W}$ is a standard mean 0, variance 1 Wiener process [11, 13].

In the simplified collinear case, where polarizer and

uniaxial axes are aligned ($n_z = 1, n_x = 0$), the projectional dynamics are the same as the regular dynamics for the m_z component of the magnetization, and are decoupled from both m_x and m_y . The problem is effectively reduced to that of a 1D stochastic differential equation characterizing the switching behavior over all possible currents [9].

As already hinted, the main complication in studying a macrospin's dynamical behavior lies in the generally complex structure of its coupled set of stochastic differential equations. Equation (3) is precisely a realization of such: in the case of collinearity between uniaxial and polarizer axes, the evolution equation for $m_z \equiv q$ doesn't depend on any of the other two magnetization components. The moment any such symmetry is broken, or more complex energy landscapes are considered (such as considering biaxial anisotropy scenarios), the full set of coupled equations (see (3) in case of general, non-zero tilt) must be considered.

The evolution of a nanomagnet is expected to operate in a regime where the nonconservative dynamics act on timescales that are much longer than that of the energy-conserving part of the hamiltonian. This can be established by noting first that currents I governing the criticality of (3) are $O(1)$ and, second, all terms with the exception of the first in (1) are of order α or higher. As such, for $\alpha \ll 1$, the two evolution timescales are separated. Trajectories then should remain close to stable periodic Hamiltonian orbits, and slowly drift from one orbit to another due to damping, STT and thermal noise. In [9], the authors addressed the problem of broken symmetries due to the presence of tilt by averaging equation (3) over constant energy trajectories. In doing so, they again retained a 1D stochastic differential equation and solved its associated mean first passage time problem. This approach, though, is just a particular example of a more general analysis which can be applied to macrospin dynamics.

Take as an example the form of the energy landscape in (2) in the absence of applied magnetic fields and ask how it evolves in time. Taking a time derivative and using the definition of q , one finds:

$$\dot{\epsilon} \equiv \frac{\dot{U}}{K} = -2q\dot{q}. \quad (4)$$

Combining (3) and (4) and averaging the dynamics over constant energy trajectories leads to a diffusion equation in energy space [4, 14, 15]. Such an equation is one dimensional and can be defined independently of the complexity of the energy landscape for any generalized macrospin system. In our particular case, the averaging is very straightforward to accomplish since constant energy trajectories ($\alpha \rightarrow 0, I \rightarrow 0, \xi \rightarrow \infty$) are simple circular librations around the uniaxial anisotropy axis with $q = \text{sgn}(q)\sqrt{|\epsilon|}$. Proceeding with the averaging and noting that $\langle q^2 s \rangle = \langle q m_y \rangle = 0$ due to the geometrical structure of the constant energy orbit, we find for states

starting antiparallel to the uniaxial anisotropy axis:

$$|\dot{\epsilon}| = 2\alpha\sqrt{|\epsilon|(1-|\epsilon|)}(\sqrt{|\epsilon|} - In_z) + 2\sqrt{\frac{\alpha}{\xi}}|\epsilon|(1-|\epsilon|) \circ \dot{W}. \quad (5)$$

Two fundamental properties of this energy space evolution are immediately seen. The first is that $In_z = 1$ behaves as a crossover value above which all dynamics prefer evolving towards the parallel state independently of noise. Accordingly, this value of In_z is hereafter denoted as the “critical current”. Analogously, the thermal regime is characterized by sub-critical current values ($In_z \ll 1$). The second is that the angular tilt between uniaxial and polarizer axes factors in only through the term n_z multiplying the current I . As such, as the angular tilt is varied, dynamics are going to differ only up to a rescaling of the current I and, beyond that, all other properties of the dynamics will be functionally identical. This was one of the main results shown in [9] where the authors averaged (3) along constant energy trajectories.

The thermally assisted properties are then easily understood by studying the mean first passage time over the effective barrier to the dynamics of $|\epsilon|$ analogously to what has been done in the literature. Instead, we consider another method (initially due to Friedlin and Wentzell [16]) to extract the exponential scaling behavior of the mean first passage time without resorting to the full mean first passage time problem. Formally, given a Langevin equation $\dot{x} = f(x) + g(x) \circ \dot{W}$, the Wiener process $\dot{W}$ can be solved at each instant in time. At each such instant, the probability of a Gaussian-distributed random kick can be written as:

$$P[\dot{W}]_t = \exp\left[-\frac{1}{2}|\dot{W}|^2\right] = \exp\left[-\frac{1}{2}\left(\frac{\dot{x} - f(x)}{g(x)}\right)^2\right]. \quad (6)$$

The probability of specific realization of a stochastic path will then simply be the product of the probabilities of all the random kicks that the path witnessed. As such the probability of a path starting in some point A and ending in B in time T will be:

$$P[A \rightarrow B] = \exp\left[-\int_0^T dt \frac{1}{2}\left(\frac{\dot{x} - f(x)}{g(x)}\right)^2\right]. \quad (7)$$

The most likely trajectory starting in A and ending in B in time T will be that which maximizes its probability of realization, or conversely, that which minimizes the F-W action:

$$S_{FW} = \int_0^T dt \frac{1}{2}\left(\frac{\dot{x} - f(x)}{g(x)}\right)^2. \quad (8)$$

Finding the action of such a trajectory is then a standard Hamilton-Jacobi problem:

$$\Delta S_{FW} = S_{FW}(B) - S_{FW}(A) = -2 \int_A^B \frac{f(x)}{g^2(x)} dx. \quad (9)$$

We are interested in the F-W action of the most probable trajectory starting in $|\epsilon| = 1$ and ending at the saddlepoint of the deterministic dynamics: $|\epsilon| = I^2$ (we specialize to the case $n_z = 1$ since all other cases are immediately reobtained by rescaling). Plugging (5) into (9), one finds that:

$$\Delta S_{FW} = \xi \int_{I^2}^1 \frac{\sqrt{|\epsilon|} - I}{\sqrt{|\epsilon|}} d|\epsilon| = \xi(1 - I)^2. \quad (10)$$

The exponential scaling between mean switching time and current is then $\tau \propto \exp(\xi(1 - I)^2)$ [8, 9].

To verify this result, we numerically solved the full stochastic LLG equation (1) by using a standard second order Heun scheme to ensure proper convergence to the Stratonovich calculus [17]. As mentioned above, the nanomagnet is initially in thermal equilibrium at a temperature T in one of its two possible stable states at the start of the simulation ($\tau = 0$), when the current is applied. At each time step, the random kicks are generated with strength given by

$$D = \frac{\alpha k_B T}{2K(1 + \alpha^2)} = \frac{\alpha}{2(1 + \alpha^2)\xi} \quad (11)$$

which is obtained by imposing the fluctuation-dissipation theorem in the absence of applied currents. Such a diffusion constant is valid as long as the magnetic sample is in equilibrium with the thermal bath and effects due to Joule heating are neglected.

As already discussed, upon breaking the symmetry of the uniaxial problem by introducing a tilt between uniaxial and polarizer axes, the scalings should remain identical up to a substitution $I \rightarrow In_z$. Furthermore, analogously to the collinear limit, one can again define a critical current I_c as the current above which all initial magnetic configurations will switch deterministically. This has already been derived elsewhere in the literature [7] and can be shown to give $I_c = 1/\cos(\omega)$, where ω is the angular tilt between uniaxial and polarizer axes. This in turn automatically implies that $n_z I = I/I_c$. In other words, the thermally activated dynamics are the same for all angular separations up to a rescaling by their respective critical current. This result is shown in Fig. 1. It is of interest to point out how the effect of angular tilt in thermally activated spin-transfer reversal is quite different from what one gets in studying the similar phenomenon of field driven reversal. It has been shown, in fact, that upon introducing an angular separation between easy and applied field axes, the scaling exponent changes abruptly in value from 2 for the collinear case to 3/2 [18].

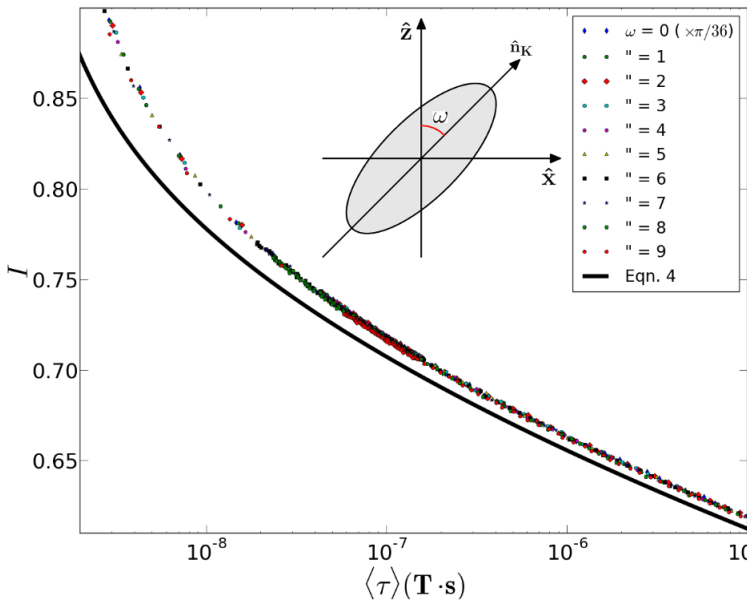


FIG. 1: Comparison of the mean switching time versus current in the sub-critical low current regime for different values of angular separation between polarizer and easy axes, ω , ranging from 0 to $\pi/4$. All critical currents have been rescaled to 1. Times are shown in units of $(s \cdot T)$ where T stands for Tesla: real time is obtained upon division by H_K . Black curve is theoretical fit from [9] where the exponential scaling behavior $\tau \propto \exp(\xi(1 - I)^2)$ was obtained by other means. It is apparent that, up to a current rescaling, the mean switching time vs applied current is independent of ω .

These results have important implications for the analysis of experimental data in which measurements of the

switching time versus current pulse amplitude are used to determine the energy barrier to magnetization reversal. Clearly, the correct asymptotic scaling form is essential to properly determine the energy barrier to reversal. The energy barrier, in turn, is very important in assessing the thermal stability of magnetic states of thin film elements that are being developed for long term data storage in STT-MRAM. Further work should address how these results extend to systems with easy plane anisotropy and situations in which the nanomagnet has internal degrees of freedom, leading to a break down of the macrospin approximation. The method exposed allows to treat analytically even more complex dynamics where other anisotropy contributions wish to be taken into account. To keep the exposition as linear as possible, we have refrained from solving the full mean first passage time problem associated to equation (5). Doing so is straightforward and proceeds exactly along the lines of what was shown in [9]. The one advantage of solving the full first passage time is that one is capable of extracting information on the exponential prefactor for the reversal time scalings. We will address the application of this methodology to the full biaxial anisotropy model in the presence of spin-torque and thermal noise in a future publication.

Acknowledgments

The authors would like to acknowledge A. MacFadyen and J. Z. Sun for many useful discussions and comments leading to this paper. This research was supported by NSF-DMR-100657 and PHY0965015.

-
- [1] J. Slonczewski, J. Magn. Magn. Mater. **159**, L1 (1996).
 - [2] L. Berger, Physical Review B **54**, 9353 (1996).
 - [3] A. Brataas, A. D. Kent, H. Ohno, Nature Materials **11**, 372 (2012).
 - [4] D. M. Apalkov and P. B. Visscher, Phys. Rev. B **72**, 180405R (2005).
 - [5] R. H. Koch, J. A. Katine, and J. Z. Sun, Phys. Rev. Lett. **92**, 8 (2004).
 - [6] Z. Li and S. Zhang, Phys. Rev. B **69**, 134416 (2004).
 - [7] J. Z. Sun, Phys. Rev. B **62**, 1 (2000).
 - [8] T. Taniguchi and H. Imamura, Phys. Rev. B **83**, 054432 (2011).
 - [9] D. Pinna, Aditi Mitra, D. L. Stein, and A. D. Kent, arXiv:1205.6509 (2012).
 - [10] W. F. Brown, Phys. Rev. **135**, 5 (1963).
 - [11] J. L. Garcia-Palacios and F. J. Lazaro, Phys. Rev. B **58**, 22 (1998).
 - [12] D. Bedau *et al.*, Appl. Phys. Lett. **97**, 262502 (2010).
 - [13] I. Karatsas and S. Shreve, *Brownian Motion and Stochastic Calculus*, 2nd ed. (Springer-Verlag, New York, 1997).
 - [14] K. Newhall and E. Vanden-Eijnden, arXiv:1210.6253 (2012).
 - [15] G. Bertotti, I. Mayergoyz, and C. Serpico, *Nonlinear Magnetization Dynamics in Nanosystems* (Elsevier, Oxford, UK, 2009).
 - [16] M. I. Freidlin and A. D. Wentzell *Random Perturbations of Dynamical Systems* (Springer, New York, 1991).
 - [17] W. Rumelin, SIAM Journal on Numerical Analysis **19**, 3 (1982), pp. 604-613.
 - [18] W. T. Coffey, Phys. Rev. B **58**, 3249 (1998).